


RAPIDRH
*Fast, Accurate Moisture Test for Concrete Floors

**A COMPREHENSIVE GUIDE
TO MOISTURE TESTING**
PREPARED BY WAGNER METERS



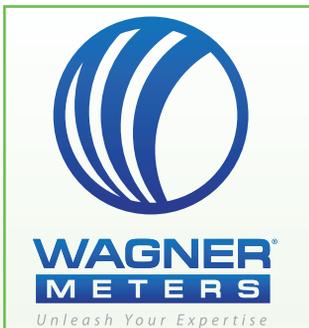

Accurate measurement of moisture levels in a concrete slab, wood subfloor, and/or wood floors is the most important step in mitigating or alleviating flooring failures. Regardless of the measurement tools you use, Wagner Meters has prepared this resource booklet to help you gain a basic understanding of the process and rationale for testing moisture levels in these different areas. We hope this guide will lessen your likelihood of financial losses resulting from preventable flooring failures.

What You Should Know about Concrete and Moisture

TEST FOR MOISTURE BEFORE INSTALLATION TO AVOID FLOORING FAILURE

Every flooring and general contractor is best served by having a basic understanding of the importance and proper protocol for testing moisture levels in concrete. Without this knowledge, a contractor faces a greater likelihood of flooring failures which may lead to wasted time and financial loss.

All types of flooring are susceptible to failure if moisture conditions are not properly monitored and maintained. When the subfloor is concrete, a moisture problem may begin long before the flooring is installed. If the concrete slab has not been properly dried and cured before the flooring is installed, moisture problems are almost guaranteed. What's more, moisture-related problems in flooring can also raise health and safety risks resulting from mildew, mold, gaps, bumps and unsecured flooring.

Having to remediate a flooring failure or worse, having to correct a concrete subsurface will increase project costs and possibly tarnish your reputation. That's why it's so important to learn to identify and correct moisture problems during the installation process, eliminating moisture problems so they don't lead to unnecessary and costly repairs of an entire floor system.

Fortunately there are some preventive measures to greatly reduce the risks of excess moisture in concrete slabs and failures to subsequently applied flooring or coating. But in order to properly understand the ideal conditions for flooring installation, some basic knowledge about concrete is important.

THE DIFFERENCE BETWEEN CEMENT AND CONCRETE

You may hear “cement” and “concrete” used interchangeably but they are not the same thing. Cement powder is the (typically) grey powder added to the concrete mix that binds all the components together. Cement is only one of the ingredients of concrete. Sand, water, and rocks (or other aggregates) are mixed with cement powder to form the finished product – concrete.

There are two basic types of cement: hydraulic and anhydrous. A common cement like Portland cement is a hydraulic cement. It hardens regardless of surrounding moisture conditions. The chemical reactions that



bind hydraulic cement can even occur underwater! On the other hand, anhydrous cements, like gypsum plaster, must be dry to keep their strength. Both of these kinds of cement are blended with additives such as fly ash, lime, silica fume, blast furnace slag and others to give a variety of strengths and colors.

Concrete is formed when the various ingredients are combined (cement, sand, water and aggregate) to create a chemical reaction that binds the materials together. In a 4-inch slab, it takes approximately four weeks for this chemical process to be complete. This is the process known as “curing.” But a cured slab may still be holding a significant amount (approximately two thirds) of the moisture from the original concrete mixture.

Drying continues after curing is complete through a process that moves moisture to the surface of the slab to then evaporate away and be replaced by more moisture drawn up through the entire slab. If the slab has cured, but not dried, it is certainly not ready for a flooring installation. And even “dry” may not be dry enough because the drying process may be greatly impacted by environmental conditions like temperature and air humidity. The only way to be sure a slab is dry enough to apply a floor covering is through adequate moisture testing.

WHY ACCURATE MOISTURE TESTING IS CRITICAL

Accurate moisture testing is critical to understanding the complete moisture levels of any concrete slab. It's not enough to perform only one test at the surface of the slab to make a go or no-go decision about installing flooring. Different areas of a slab may dry unevenly so it's necessary to test several different spots on each slab including spots below the surface of the slab (at service conditions). ASTM International has provided several standards related to testing for moisture with two different test methods before installing flooring over a concrete slab: in situ probes (ASTM F2170) and calcium chloride testing (ASTM F1869).

The calcium chloride test method is used to determine the moisture vapor emission rate (or MVER) from a concrete slab. The test involves sealing a small dish of calcium chloride on a clean section of concrete under a plastic dome. The salt absorbs moisture in that environment (and presumably coming from the concrete slab) and the weight gain after three days is used to calculate the MVER. While this method is still specified by some flooring manufacturers, architects and adhesive manufacturers, the calcium chloride test really only tests the surface conditions of the slab. (Note: calcium chloride testing has also been disallowed as an appropriate method for testing on lightweight concrete.)

To test the moisture conditions within the slab, best indicator of the overall



moisture condition of the floor is relative humidity (RH) testing using in situ probes, ASTM F2170. A series of test holes are drilled into the slab and a small probe is placed into the hole where it is allowed to equilibrate with the slab before readings are taken. Research has found that placing the probe internally, at a depth of 40% of the slab's total thickness (if drying one side),

provides the best indicator of what moisture conditions will be encountered by the adhesive and finished flooring product upon installation.

Understanding the basic concepts about concrete, and correctly monitoring its RH as it dries, can significantly reduce the risk of moisture-related flooring problems.

Every professional on a building site, whether specifying the correct concrete for a given time frame, choosing the proper adhesive for the condition of the slab, or determining if it's safe to go ahead with the flooring installation, will benefit by having correct information regarding moisture levels in concrete.

Performing Correct and Accurate RH Testing

ENSURE ACCURATE MOISTURE READINGS FOR YOUR CONCRETE SLABS

To prevent a moisture-related failure to a floor covering or coating installation, it is necessary for the slab to be at the proper moisture level. Therefore, obtaining accurate moisture RH readings is critical. The patented Rapid RH® Smart Sensor design is superior in a number of ways to other RH test methods. For one, the Rapid RH L6 single-use sensor is permanently embedded into the concrete, making it easy to obtain fast, accurate RH readings consistent with ASTM F2170. The L6 single-use sensor is ideal for all users, including flooring installers and general contractors.

Only the Rapid RH offers a choice of either a single-use or reusable sensor. Other manufacturers use some type of reusable probe, inserted into a plastic “sleeve” in the hole. Reusable probes generally require more time and careful use in order to obtain accurate results while meeting the ASTM F2170 requirements. Improper use of reusable probes can leave you at risk of a moisture-related flooring failure.



Regardless of the methods or tools you use, we want you to be aware of the following issues, so you can obtain accurate RH readings and mitigate your risk of a flooring failure.

PROBLEMS WITH “LEAPFROGGING”

Per ASTM F2170*, RH probes require 24 hours to equilibrate in the concrete slab before official, documentable readings can be taken. Some users of reusable probes expect to move probes quickly from hole to hole (leapfrogging) without giving the probes ample equilibration time. With leapfrogging, you can expect inaccurate readings, usually significantly underestimating the true RH. With the patented single-use Rapid RH method, you do not have to be concerned with waiting for the Rapid RH L6 sensors to equilibrate each time you need to take a reading. After the initial required equilibration time of 24 hours, you can obtain subsequent readings from each probe anytime thereafter with no wait time.

LACK OF CALIBRATION VERIFICATION

ASTM F2170 indicates that probe calibration must be verified for accuracy within 30 days of each use. All reusable RH probes eventually fall out of calibration (due to contaminants, etc). Contamination of reusable probes can lead to inaccurate readings. Section 8 in ASTM F2170 requires verification of a probe’s measurement accuracy using a salt solution or a humidity chamber.

Rapid RH sensors come with a certificate of NIST-traceable calibration. If you use the Rapid RH single-use method, you never need to be concerned with verifying calibration and the associated costs. Or for anyone who prefers a reusable sensor, the Rapid RH 5.0 reusable is uniquely designed for fast calibration checks using the innovative EasyCare CalCheck®, a feature that moisture inspectors and others who perform frequent concrete moisture tests will appreciate.

OUT OF COMPLIANCE RH TESTING EQUIPMENT

ASTM F2170 requires that RH readings be performed at 40% depth in the concrete slab (if the slab is drying from one side; 20% if drying from two sides). The standard is also very specific that sensors be located within 5/8 inch of the bottom of the hole, have isolation fins at the bottom of the “sleeve”, between the

sleeve and the concrete, to ensure that RH readings take place at the proper depth. Lastly, the “sleeve” must line the entire depth of the hole. Make sure you only use equipment that conforms to the specifications.

The design of the Rapid RH ensures the user can easily obtain readings at the correct depth. Just drill the hole to the correct depth and insert the Rapid RH Smart Sensor to that depth. The patented design of the Rapid RH Smart Sensor, including its small volume of air space, ensures conformance to the ASTM depth requirement while also providing very rapid equilibration times.

*Section 10.3.4 of ASTM F2170 currently states: “Allow 24 hours to achieve moisture equilibrium within the hole before making relative humidity measurements.” Wagner’s Rapid RH patented design allows for obtaining initial readings in the first 60 minutes that will generally be within 3-5% of the reading at 24 hours. The initial readings at one hour can usually give a general idea of the moisture content of the concrete for the purposes of planning. However, it is recommended that the ASTM F2170 specification is strictly adhered to.



You'll find a variety of educational and informative articles, mobile apps and videos regarding Relative Humidity Testing for Concrete Floors at www.RapidRH.com

RECOMMENDED STEPS TO COMPLY WITH ASTM F21

1. Verify that your relative humidity measuring instrument conforms to section 6 of ASTM F2170.
 - Verify NIST-traceable calibration certificate is on file.
2. Check calibration of measuring instrument per section 8 of ASTM F2170.
 - Recalibrate probes at least annually. (Does not apply to single-use Rapid RH L6.)
 - For reuseable probes, check probe calibration within 30 days of use.
 - Follow ASTM F2170 8.2.1 Calibration Check Procedure, Saturated Salt Solutions.
 - Note date on report.
3. Verify 48-hour service conditioning of concrete floor slab and the occupied air space above the floor slab per section 9 of ASTM F2170.
 - Concrete floor slab shall be at service temperature and the occupied air space above the floor slab shall be at service temperature and service relative humidity for at least 48 hours.
4. Determine number and location of test holes per section 10.1 of ASTM F2170.
 - Three test holes for the first 1000 ft² (100 m²) and at least one additional test for each additional 1000 ft² (100 m²).
 - Record total area of concrete slab and number of test holes required on report.
5. Determine depth of test holes per section 10.2 of ASTM F2170.
 - 40% of slab thickness if slab is drying from top only.

2170 STANDARDS FOR RELATIVE HUMIDITY TESTING

- 20% of slab thickness if slab is drying from top and bottom.
 - Record concrete slab thickness and depth of test holes on report.
6. Drill and prepare test holes per section 10.3 of ASTM F2170.
 - Note location of test holes on site map.
 - For Rapid RH, place serial number decal of sensor with corresponding test hole on report.
 7. Verify 24-hour moisture equilibrium period for each test hole per section 10.3.5 of ASTM F2170.
 8. Perform relative humidity measurements per section 10.5 of ASTM F2170.
 - Verify that meter reading does not drift more than 1% relative humidity over a 5 minute period.
 - A Rapid RH Total Reader® can be read immediately after insertion into each test hole since the sensor has already been equilibrated for at least 24 hours.
 - Reusable probes should equilibrate at least one (1) hour in each test hole to help ensure an accurate measurement.
 9. Record and report the results per section 11 of ASTM F2170.

We highly recommended that you obtain your own copy of ASTM F2170 at www.astm.org/Standards/F2170.htm





The Whole Flooring Picture

When working to prevent moisture-related problems with wood flooring, there are multiple layers that can contribute to moisture issues. Simply acclimating and installing the flooring product itself is only one step in a series that should be included when installing wood flooring products.

From the Ground Up

CONCRETE SLABS FOR WOOD FLOORING PROFESSIONALS

“I’m a wood flooring specialist – why would I need to know about concrete?”

When a wood floor is installed over a concrete slab (whether that includes separate subfloor or not), the moisture picture in the concrete slab can have real ramifications for the finished floor. If a new slab has not dried completely to finished specifications, that moisture will continue to wick up through the surface of the concrete and can cause anything from adhesive failure to wood warping or cupping. If an older slab has developed cracks or moist patches, those can also work their way to the surface and provide an avenue for moisture to compromise a wood floor. Even with a vapor barrier, moisture can still be an issue if the slab has not properly dried. It pays to have an understanding of concrete moisture testing.

Concrete moisture conditions are most reliably established with RH testing that uses in situ probes. Other test methods, including calcium chloride testing or the poly-film test, have proven problematic in the past and are slowly being discontinued. Other varieties of meters, like surface concrete meters, might help to determine the most likely areas for necessary RH testing, but keep in mind that surface concrete meters do not provide an in-depth picture of moisture conditions within the slab. True quantitative testing must be done to protect your flooring installation.

It pays to check what the job specs have called for, have performed the appropriate moisture testing, and have the manufacturer acceptable results on file, prior to beginning your installation. Moisture problems in the concrete slab may not ultimately be your responsibility, but left unchecked they might still end up becoming your problem.



THE WOOD SUBFLOOR

Just like moisture problems with a concrete slab subfloor, improper moisture conditions in a wooden subfloor can lead to moisture-related issues in a finished floor. Two types of moisture meters are often used to determine the moisture

content (MC) of wood subfloors: the pin-style meter and the pinless (or non-destructive) meter (see “Moisture Content Management During Installation”). Just like the final wood floor, the subfloor must also be stable in terms of MC in order to prevent possible moisture-related flooring issues over time.

With either style of wood moisture meter, it is important to test several areas of a wood subfloor to be sure that the moisture conditions are acceptable for the final flooring installation. While several types of products are on the market to prevent this moisture from migrating from one layer to the next, proper moisture conditions before beginning installation help reduce the risk of flooring issues or failure.

A good rule of thumb is that the subfloor MC should be within 3-4 percentage points of the flooring to be installed before proceeding.

THE FLOORING

Before installation, wood or engineered flooring to be installed should also be checked with an accurate wood moisture meter. Several bundles should be opened and tested to ensure that the wood flooring is at the same MC throughout, and is compatible with the subfloor over which it will be installed. Like the wood subfloor, pin-style and pinless meters can give an indication of the MC to ensure a professional and long-lasting flooring installation. The advantage that pinless



meters have with wood flooring is in their damage free measuring – no pin holes means no filling or sanding on the final floor.

And of course, room conditions should also be monitored to ensure they are at service normal conditions. Even a good flooring installation with adequate moisture testing might not overcome extreme changes in

ambient temperature and humidity. But allowing the wood products to acclimate to these normal ambient conditions is one of the best recommended practices.

As the old adage says, “An ounce of prevention is worth a pound of cure.” At any stage of the flooring work, accurate moisture testing is the best defense against moisture-related problems making an appearance.

WOOD FLOORS

Wooden floors can be as durable as they are beautiful. But there's a big IF in a statement like that. Wooden floors can be as durable as they are beautiful IF they are installed properly. And any proper installation must begin with an understanding of the continuous relationship between wood and moisture.

WOOD AND WATER – A CONTINUOUS INTERACTION

As a growing tree, wood cells are like bundles of long, narrow drinking straws that help the moisture move up the length of the trunk and out through the branches and twigs. Obviously, when a tree is felled, it begins to lose moisture that is not renewed through its root system.



But even as it loses moisture, the cell structure of wood makes it possible for it to reabsorb moisture that exists as air humidity. Wood ultimately reaches a point of equilibrium (or balance) with its environment, but change the environment and the wood will lose or absorb moisture accordingly. This relationship between wood and its environment is referred to as “hygroscopic”.

How does this affect wood flooring? As moisture moves in and out of wood flooring, it will actually change dimensions depending on moisture conditions. (To see a dramatic example of this principle, try experimenting with a stalk of celery. Cut it into lengths both horizontally and vertically and place it in water for a day or two and see what happens!)

Cut wood will typically change in width and thickness, not in length because most saw cuts run vertically rather than horizontally. The degree of change will be influenced by the amount of moisture being absorbed or lost, the species of wood, the season it was harvested, the part of the tree the lumber was cut from, the width of the board and the type of saw cut used.

Moisture levels in the average household are considered to be between 6-9% and wood flooring is generally dried to this level. But regional and seasonal variations mean that even wood flooring manufactured from properly-dried lumber will need an acclimation time in the installation environment to prevent extreme changes in the finished floor. Think of this – even a change as small 1/32” per 2” board multiplied across an eight foot room equals 1 ½” of gapping or swelling.

MC is crucial to proper installation.

A NOTE ON ENGINEERED WOOD PRODUCTS

Engineered wood also needs the same acclimation time as natural wood products. During the manufacturing process, layers of wood or wood products are joined together to create the finished product. In the event that producers use layers of different wood species, the moisture management imperative is even greater. Each wood layer (even equilibrated) responds differently to changes in RH. Add the chemical and MC of industrial wood glues, and one gets a clear sense of the challenge to produce outstanding engineered flooring.

When installed, engineered wood flooring tends to be more dimensionally stable but it can still be susceptible to moisture damage. And when installed with adhesive products, MC becomes just as critical as with any other flooring product.

MOISTURE CONTENT MANAGEMENT DURING AND AFTER INSTALLATION

Because of the hygroscopic nature of wood, thorough acclimation is critical when installing wood flooring. And there are a number of tools available to help all stages of the installation process.

1. Ambient RH & Temperature Data Logger – Whether you are renovating a home or building a hospital, monitoring ambient temperature and humidity conditions at your project can help you avoid costly and time-consuming damage as well as expensive call backs later. The only way to be sure service conditions remain is constant observation and recording. The Wagner Meters Smart Logger™ monitor and the Smart Logger™ app are your eyes on the job site 24 hours a day.



2. In-Floor Moisture Monitoring – A beautiful wood floor is a significant investment. The last thing you want is for it to be destroyed by moisture. Using an in-floor monitoring device, such as the Wagner Floor Sentry, shields your investment after installation by providing ongoing monitoring of environmental conditions within your floor. The Floor Sentry is a small device that is placed inside your wood floor during installation. It then connects to an app on your smart phone to alert you to moisture issues before they can wreak havoc.



3. Wood Moisture Meters – Wood moisture meters assess MC in wood through a couple different types of underlying technology, and so are often referred to as “pin-style” or “pinless” moisture meters. Wood moisture meters can be designed or programmed for different depths of readings, as well as species settings (or adjustment tables) and a range of features designed to help maintain accurate MC assessment on the job site.

a. Pin-style moisture meters - A pin meter measures the moisture content of wood via an electrical signal between the tips of two narrow metal probes inserted into the wood. One advantage of pin meters (only those that use longer pins with insulated shafts) is that you can test at different depths. Disadvantages are the relatively small area tested with each insertion, sensitivity to wood temperature, damage to the wood surface caused by the pins, the tendency for pins to break, and inaccurate readings if pins are not inserted properly.

b. Pinless moisture meters - Pinless meters use an electromagnetic signal to penetrate the wood surface. This allows users to “scan” many board feet of wood simply and quickly without damage. Pinless meters take readings at a fixed depth and require applying adequate pressure for correct readings.

As with any measurement tool, accuracy depends on proper maintenance and use. For example, if your meter takes readings at 1 ½” depth, but your flooring is ¾” stock, the readings may reflect either ambient conditions underneath or subfloor conditions under an existing wood floor. For pin meters, if the probe’s insulation is peeling, the readings can be skewed. For pinless meters, if the sensor pad gets scratched or damaged, this can also skew readings.

Of course, a moisture meter only identifies a moisture issue in wood; it does not fix it. Moisture problems can arise if the wood did not reach equilibrium moisture content (EMC) during drying or manufacturing, if flooring installers pay little attention to the MC of the wood, if the RH of the room is not monitored before and during installation, or if the RH changes after installation. Proper attention to potential moisture issues means increased confidence in the longevity and durability of each flooring installation.

CHECK OUT
wagnermeters.com/webinar
 for the latest up-to-date webinar

Fast**ER**, **MORE** Accurate
 Moisture Test
 for Concrete Floors

RAPIDRH L6

THE BEST
 RH TEST
 JUST GOT
 BETTER

- Simplest F2170 Test
- Improved Technology and Responsiveness Especially in High RH
- Integrated Data Storage
- Lowest Cost/Test

U.S. Patent 7,231,815, 8,047,056, 9,032,791 & 9,588,092. Additional patents pending

WAGNER METERS

502-RTEST-001 REV F

GIVING FLOORING CONTRACTORS BOTH
SPEED & ACCURACY
 NEW ORION® WOOD MOISTURE METER

ORION
 WOOD MOISTURE METER
 930 CE

f t in y @WagnerMeters

wagnermeters.com
 Call (800) 585-7618